arXiv:cond-mat/9905170v1 [cond-mat.supr-con] 12 May 1999

Interlayer Conductivity in the Superconductor $Tl_2Ba_2CuO_{6+\delta}$: Energetics and Energy Scales

A.S. Katz,[1] S.I. Woods,[1] E.J. Singley,[1] T.W. Li,[2*] M. Xu,[3*] D.G. Hinks,[2] R.C. Dynes,[1] and D.N. Basov[1]

[1]*Department of Physics, University of California, San Diego; La Jolla, CA 92093-0319*

[2]*Department of Materials Science, Argonne National Laboratory, Argonne, IL 60439*

[3]*James Franck Institute, University of Chicago, Chicago, IL 60637*

Abstract

We report on infrared studies of the c-axis electrodynamics of $Tl_2Ba_2CuO_{6+\delta}$ crystals. A sum rule analysis reveals spectral weight shifts that can be interpreted as a kinetic energy change at the superconducting transition. In optimally doped crystals, showing an incoherent normal state response, the kinetic energy is lowered at $T < T_c$, but no significant change is found in the over-doped samples, which have more coherent conductivity at $T > T_c$.

78.30.-j, 74.72.Fq, 74.62.Dh, 74.25.Gz

Typeset using REVTEX

Despite extensive experimental effort in high-T_c superconductivity over the last decade very little is known about the microscopic roots of the condensation energy E_c in this class of materials. In conventional superconducting metals E_c is due to the *reduction* of the potential energy, which overwhelms the *increase* of the electronic kinetic energy [1]. Several models of high-T_c superconductivity propose entirely different energetics of E_c with the superconducting state being driven by changes of the Coulomb energy [2], exchange energy [3,4] or kinetic energy [5–9]. Existing experimental results are inconclusive [10–12,3].

A variety of models enable inference of the electronic kinetic energy from a sum rule analysis of the complex optical conductivity $\sigma(\omega) = \sigma_1(\omega) + i\sigma_2(\omega)$ [13]. A partial sum rule relates the integral of $\sigma_1(\omega)$ over a limited energy range W to the kinetic energy $-\alpha$:

$$\int_0^W d\omega\, \sigma_1(\omega) = -\alpha. \tag{1}$$

For the case of a superconductor Eq. (1) can be rephrased in the form of a modified Ferrel-Glover-Tinkham (FGT) sum rule to yield the kinetic energy sum rule [7,8,14]:

$$\rho_s = [N_n - N_s] + [\alpha_n - \alpha_s] \tag{2}$$

In Eq. (2), ρ_s is the superfluid density that quantifies the spectral weight under the superconducting δ-function [15]. Integrals $N_n(\omega) = \int_{0^+}^{\omega} d\omega' \sigma_1(\omega', T > T_c)$ and $N_s(\omega) = \int_{0^+}^{\omega} d\omega' \sigma_1(\omega', T \ll T_c)$ are proportional to the number of carriers participating in absorption above and below T_c. The magnitude of $\rho_s = 4\pi\omega\sigma_2(\omega \to 0)$ and $[N_n - N_s]$ are obtained independently from the optical constants [12]. Typically, the $[N_n - N_s]$ integrals converge at energies below 10-15 $k_B T_c$ [16]. A comparison of the magnitudes of ρ_s and $[N_n - N_s]$ then provides a basis for an experimental probe of the kinetic energy change $\Delta\alpha = [\alpha_n - \alpha_s]$. Physically, the non-vanishing magnitude of $\Delta\alpha$ implies that changes of the low-energy spectral weight in Eq. (1) are compensated by readjustment of interband transitions at $\omega > W$ so that the global sum rule $\int_0^{\infty} d\omega\, \sigma_1(\omega) = \frac{\pi n e^2}{2m_e}$ is satisfied.

Recently, we found a $\rho_s > [N_n - N_s]$ inequality in the interlayer conductivity of a variety of cuprates indicating that the superconducting condensate is collected from an interband-scale energy range [12]. This result can be interpreted in terms of a reduction of the kinetic energy below T_c. In this paper we explore the connection between the development of coherence in the interlayer conductivity and the anomalous behavior of the c-axis superconducting condensate in $Tl_2Ba_2CuO_{6+\delta}$ (Tl-2201). We found that the energy scale associated with superconductivity extended to the interband region when the normal state conductivity across the layers was nearly blocked. Once the interlayer transport above T_c became more coherent, the FGT sum rule approached exhaustion at energies below $\sim$5 $k_B T_c$ suggesting that any kinetic energy change was very small or nonexistent.

$Tl_2Ba_2CuO_{6+\delta}$ is an ideal material for studying the over-doped regime of the phase diagram in which a variety of cuprates reveal a crossover to a more coherent response. Highly over-doped crystals of Tl-2201 have nearly identical chemical composition to the optimally doped phase since a less than 2% change in the oxygen content is required to suppress T_c from the maximum value of $T_c \simeq 90$ K down to less than 4 K [17]. Crystal preparation is described elsewhere [10]. Typical crystal dimensions were nominally 0.8 mm x 0.8 mm x 0.04 mm. Mosaics of several specimens with similar T_c and ΔT_c (determined from magnetization measurements) were prepared and polished along a face parallel to the

c-axis. The polished surfaces were smooth, black, and shiny. Infrared reflectance, $R_c(\omega)$, was measured with $E \parallel c$ polarized light in the frequency range from 16 to 15,000 cm^{-1}. Spectra taken at different temperatures had a relative experimental uncertainty of less than 0.5%.

In Fig. 1, we show the raw reflectance results for the optimally and over-doped crystals. The $E \parallel c$ reflectance of both samples over the range of 80 to 2000 cm^{-1} (10 to 250 meV) resembled an ionic insulator with a low reflectivity punctuated by phonon peaks. Both samples showed a plasma edge below T_c. Classical electrodynamics describes the development of this plasma edge since superconducting currents flow along all crystallographic directions [18]. In the optimally doped sample ($T_c = 81$ K, $\Delta T_c \simeq 8$ to 10 K) the plasma edge grew out of an apparently insulating normal state spectrum. In the over-doped sample ($T_c = 32$ K, $\Delta T_c \simeq 5$ K) we found a "metallic" up-turn in $R_c(\omega)$ measured above T_c, consistent with more coherent delocalized behavior. Below T_c, the reflectance continued to rise, and the plasma edge developed a characteristic minimum at a frequency position of $\omega = 49$ cm^{-1}. The minimum in reflectance was shifted to higher frequencies compared to $\omega = 37$ cm^{-1} in the optimally doped case and was less sharply defined.

The raw $E \parallel c$ reflectance data was transformed using the Kramers-Kronig relations to determine the complex conductivity. Extrapolations of the reflectance data to low and high frequencies, required for the Kramers-Kronig integrals, did not strongly affect the results in the frequency range where measured data exists. The real part of the conductivity spectra were dominated by strong phonon peaks (Fig. 2). Three of the modes at 85, 151, 360 cm^{-1} were unaffected by doping; the highest frequency mode softened from 602 cm^{-1} in the optimally doped crystal down to 595 cm^{-1} in the over-doped sample. The electronic background of the conductivity of the optimally doped sample was nearly flat and featureless for temperatures above and below T_c. The response of the over-doped crystal was different. The conductivity below 80 cm^{-1} showed a Drude-like behavior steadily rising out of a $\sim$5 (Ω cm)$^{-1}$ background. Below T_c, this "metallic" response diminished as temperature was lowered. By T = 5 K, it effectively vanished, and the conductivity (ignoring phonon peaks) was nearly frequency independent. Just above T_c, the dc conductivity of the over-doped sample at T = 35 K (obtained from the extrapolation of $\sigma_1(\omega)$ to $\omega = 0$) was $\sim$15 (Ω cm)$^{-1}$. This is roughly a factor of 3 higher than the value obtained for optimally doped Tl-2201 crystals. It has been established that increasing oxygen content causes the c-axis to contract [19]. This closer spacing of the CuO_2 planes favors enhanced interlayer coupling and likely leads to the more coherent behavior of the conductivity. It is important to emphasize, however, that the c-axis conductivity is still two orders of magnitude smaller than the in-plane dc conductivity, and it is 4 to 6 orders of magnitude smaller than the conductivity of conventional metals.

Using the complex conductivity spectra above and below T_c, we can identify the spectral origins of the superfluid condensate. In all of our measurements, the conductivity at $T < T_c$ was suppressed compared to spectra taken at $T \simeq T_c$, but we saw no evidence of a classical superconducting gap Δ for $T \ll T_c$. The absolute value of $\sigma_1(\omega)$ persisted well above the noise level down to the lowest measured frequencies, behavior consistent with gaplessness. To quantify the transfer of spectral weight below T_c, we plotted the ratio $[N_n(\omega) - N_s(\omega)]/\rho_s$ as a function of ω in Fig. 3 [12]. The superfluid density ρ_s was determined from the extrapolation of $\omega\sigma_2(\omega, T)$ to $\omega = 0$ for $T \ll T_c$, a procedure that does not require model-dependent

assumptions [20]. The frequency dependence of $[N_n(\omega) - N_s(\omega)]/\rho_s$ unfolds the sum rule integrals. In the optimally doped sample, the ratio rose slowly and saturated near a value of about 0.6 at $\omega \simeq 30 - 40$ meV. The energy interval in Fig. 3 corresponds to $\sim$22 $k_B T_c$, more than sufficient for the conventional FGT sum rule. The data for the optimally doped sample implied that a significant portion of ρ_s was accumulated from energies above 0.15 eV. In contrast, in over-doped Tl-2201 the dominant fraction of the superfluid density was collected from the far-infrared, low energy region. Within our experimental uncertainty, at least 80 to 90% of ρ_s was accumulated from energies as small as 4 - 5 $k_B T_c$ [21]. Comparison of the data plotted in Fig. 2 and in Fig. 3 suggests that the behavior of the conductivity above T_c determines the energy scales from which the superconducting condensate is collected. In the case of the over-doped crystal there is no need to extend integration of the conductivity to mid-infrared and near-infrared energies in order to account for the magnitude of ρ_s since the required spectral weight is readily available at low energies.

If Eq. (2) is chosen as the basis for data interpretation, then the $\rho_s > [N_n - N_s]$ inequality observed in the optimally doped crystal implies a reduction of the electronic kinetic energy below T_c. The reduction of the kinetic energy can be understood by noting that the charge carriers are nearly confined to the CuO_2 planes above T_c whereas in the superconducting state *paired* charges move more easily between the layers. On the contrary, the over-doped sample, which revealed a more coherent c-axis response (Drude-like upturn of $\sigma_1(\omega)$ and enhanced dc conductivity), showed $\Delta\alpha \simeq 0$ within our error bars. The data suggested that a kinetic energy change is observed only if deconfinement of the charge carriers occurs by virtue of pair tunneling below T_c. If the charge carriers were already delocalized in the normal state (even with very low plasma frequencies), then the magnitude of $\Delta\alpha$ is vanishingly small. The same trend was observed in the c-axis response of the $YBa_2Cu_3O_x$ (YBCO) family. The discrepancy between $[N_n(\omega) - N_s(\omega)]$ and ρ_s, suggesting a lowering of the kinetic energy, was most extreme in $YBa_2Cu_3O_{6.53}$. As the oxygen content was raised, the excess spectral weight appeared in the lower energy part of $\sigma_1(\omega, T > T_c)$ spectra. The $[N_n(\omega) - N_s(\omega)]/\rho_s$ ratio with integration limited up to 10-15 $k_B T_c$ was near unity for $YBa_2Cu_3O_{6.85}$ and higher doping levels indicating that $\Delta\alpha$ became vanishingly small [22].

Further analysis of the over-doped Tl-2201 crystal showed a lower energy scale associated with superconductivity. It has been experimentally observed in a wide variety of cuprates that the magnitude of the c-axis penetration depth $\lambda_c = c/\sqrt{\rho_s}$ is related to the dc conductivity σ_{dc} at $T \simeq T_c$ by the relationship

$$\lambda_c^{-2} = \frac{1}{\hbar c^2} \Omega_S \, \sigma_{dc}(T \simeq T_c), \tag{3}$$

where Ω_S is an energy scale associated with superconductivity [23–25,8]. Eq. (3) may be obtained either by modeling a dirty limit bulk superconductor or by treating the anisotropic cuprates as a weakly coupled stack of intrinsic Josephson junctions. Those models find $\Omega_S = 4\pi^2\Delta$. In our experiments, λ_c remained nearly unchanged [20] whereas the c-axis dc conductivity increased by a factor of $\sim$3 in the over-doped crystals. If Eq. (3) holds true, then Ω_S must be reduced in the over-doped regime in order to keep the penetration depth constant. Supporting evidence that Ω_S is indeed reduced for over-doped Tl- 2201 comes from Raman scattering measurements on optimally and over-doped Tl-2201 which found that a spectral feature attributed to the superconducting energy gap 2Δ shifted down in frequency from $\sim$350 cm^{-1} in optimally doped Tl-2201 to $\sim$105 cm^{-1} in an over-doped sample as

T_c fell from 78 K to 37 K [26,27]. c-Axis polarized Raman scattering in $Bi_2Sr_2CaCu_2O_{8+\delta}$ (Bi-2212) single crystals also showed an energy scale that diminished in over-doped samples [28]. The lower energy scale of the superfluid condensation seen in Fig. 3 is consistent with a reduction in Ω_S [29].

Several important distinctions of over-doped phases from the optimally-doped counterparts have been observed in different families of the cuprates. Raman spectroscopy showed both in Tl-2201 and Bi-2212 single crystals highly anisotropic energy gaps at optimal doping but revealed a crossover to isotropic behavior in over-doped samples [26]. Consistent with this latter result, angular resolved photoemission (ARPES) on Bi-2212 found that the Fermi surface nodes vanished in the over-doped regime [31]. Thus, both Raman and ARPES studies suggested a trend towards the development of a more isotropic superconducting state in over-doped crystals. We observed a more conventional superfluid response in over-doped Tl-2201 compared to the optimally-doped sample. Phase sensitive measurements of the order parameter in over-doped materials are needed to determine if the above observations are associated with the development of an s-component of the order parameter. An s-wave component in the order parameter in the over-doped regime is possible within the stripe-based models [9].

Based on the existing experimental results we were unable to correlate changes in the kinetic energy with the critical temperature of the studied superconductors. In the Tl-2201 series, $\Delta\alpha$ is largest in the optimally-doped crystals. The YBCO data, however, revealed large changes of α in the underdoped regime whereas in the optimally doped samples the effect was negligible [12]. The common parameter determining the kinetic energy change for both series of crystals appears to be the dc conductivity. It remains to be seen if the absolute value of $\Delta\alpha$ is sufficient to account for the condensation energy determined from specific heat measurements [10,11,8].

In conclusion, we employed infrared spectroscopy to examine the energy scales of superconducting state in Tl-2201. We found that the superfluid spectral weight was accumulated from lower energies when the c-axis conductivity showed a more coherent, delocalized response. Using the modified FGT sum rule we could extract kinetic energy changes and correlate this change to the normal state c-axis conductivity.

We thank D.A. Kossenko for technical assistance. Work at UCSD supported by NSF Grant, DMR-9875980, AFOSR Grant F4962-098-0264, DOE Contract DE-AC02-98CH10886, the Sloan Foundation, and the Research Corporation. Work at Argonne supported by NSF Grant DMR 91-20000 and by DOE Contract W-31-109-ENG-38.

REFERENCES

* Present Address: Lucent Technologies, 2000 North Naperville Road, Naperville, IL 60566.

[1] M.Tinkham, *Introduction to Superconductivity*, McGraw-Hill, Inc. (1994)

[2] A.J. Leggett, J.Phys. Chem. Solids **59**, 1729 (1998).

[3] E. Demler, and S.-C. Zhang, Nature **396**, 733 (1998).

[4] D.J. Scalapino and S.R. White, cond-mat/9805075.

[5] J.E. Hirsch, Phys. Rev. Lett. **59**, 228 (1987).

[6] P.W. Anderson, *The Theory of Superconductivity in the High-T_c Cuprates*, (Princeton University Press, Princeton, 1998); P.W. Anderson, *Science* **279**, 1196 (1998).

[7] J.E. Hirsch, Physica C **199**, 305 (1992).

[8] S. Chakravarty, Eur. Phys. J. **B5**, 337 (1998); S. Chakravarty, H.-Y. Kee, and E. Abrahams, Phys. Rev. Lett. **82**, 2366 (1999).

[9] V.J Emery and S.A. Kivelson, cond-mat/9809083.

[10] K.A. Moler *et al.*, Science **279**, 1193 (1998).

[11] A.A. Tsvetkov *et al.*, Nature **395**, 360 (1998).

[12] D.N. Basov *et al.*, Science **283**, 49 (1999).

[13] P.F. Maldague, Phys. Rev. B **16**, 2437 (1977); B.S. Shastry and B. Sutherland, Phys. Rev. Lett. **65**, 243 (1990), M.V. Klein and G. Blumberg, Science **283**, 42 (1999).

[14] E.H. Kim, Phys. Rev. B **58**, 2452 (1998).

[15] We define $\rho_s = 4\pi e^2 n_s/m^*$, where e is the electron charge, n_s is the density of superconducting carriers, and m^* is their mass. This definition implies ρ_s has dimensions of the plasma frequency squared (cm^{-2}).

[16] The energy scale of the order of 15 kT_c is sufficient to satisfy the FGT sum rule in the case of *ab*-plane conductivity of most cuprates, including optimally doped Tl-2201 (Z. Schlesinger *et al.* Phys. Rev. B **41**, 11237 (1990); D.N. Basov, *et al.*, Phys. Rev. Lett. **74**, 598 (1995); A.V. Puchkov *et al.* Phys. Rev. B **51**, 3312 (1995)).

[17] Y. Kubo *et al.*, Phys. Rev. B **43**, 7875 (1991).

[18] J. Schutzmann *et al.*, Phys. Rev. B **55**, 11118, (1997).

[19] C. Opagiste *et al*, Physica C **213**, 17 (1993); C.A. Wang *et al.*, Physica C **262**, 98 (1996).

[20] We obtained a value for the superconducting plasma frequency, $\omega_{ps} = \sqrt{\rho_s} = 134 \pm 5\ \mathrm{cm}^{-1}$, and the *c*-axis penetration depth, $\lambda_c = c/\sqrt{\rho_s} = 11.5 \pm 0.5\ \mu$m. These are nearly the same values obtained for optimally doped Tl-2201 ($\omega_{ps} = 130\ \mathrm{cm}^{-1}$, $\lambda_c = 12\mu$m). Moler *et al.* (unpublished) also observed that the *c*-axis penetration depths of optimally and over-doped Tl-2201 crystals are nearly equal, although their values were about 20% larger.

[21] The peaks at approximately 45 and 75 meV in the over-doped sample data in Fig. 3 are due to the slight temperature dependence of unsubtracted *c*-axis phonons. The phonons have been removed in the optimally doped data since they showed a much stronger temperature dependence. Data with phonons can be found in [12].

[22] D.N. Basov (unpublished).

[23] D.N. Basov *et al.*, Phys. Rev. B **50**, 3511 (1994).

[24] S. Uchida, K. Tamasaku, Physica **C 293**, 1 (1997).

[25] J.R. Kirtley, K.A. Moler, G. Villard, and A. Maignan, Phys. Rev. Lett. **81**, 2140 (1998).

[26] C. Kendziora, R.J. Kelley, and M. Onellion, Phys. Rev. Lett. **77**, 727 (1996); K.C. Hewitt *el at., ibid.* **78**, 4891 (1997); C. Kendziora and M. Onellion *ibid.* **78**, 4892 (1997).
[27] M. Kang *et al.*, Phys. Rev. Lett. **77**, 4434 (1996).
[28] H.L. Liu *et al.*, Phys. Rev. Lett. **82**, 3524 (1999).
[29] Data shown in Fig. 3 suggested a stronger suppression of the energy scale from which the condensate is collected than a factor of 3 inferred from Eq. 3. This equation implies that the entire spectral weight contained in the normal state conductivity at $\omega < \Omega_S$ is transferred to the δ-function in superconducting state. This is a correct assumption for a BCS superconductor, but in cuprates only a small fraction of the normal state spectral weight goes into condensate (see Fig. 2).
[30] L. Ozyuzer *et al.*, Phys. Rev. B **57**, R3245 (1998)
[31] R.J. Kelley *et al.*, Science **271**, 1255 (1996).

FIGURES

FIG. 1. Reflectance of Tl-2201 measured with $E \parallel c$ polarization of incident radiation. Left panel: The optimally doped sample develops a superconducting plasma edge out of an apparently insulating spectrum for $T < T_c$. Right panel: At the lowest energies, the over-doped sample shows continuously increasing reflectance above and below T_c.

FIG. 2. Real part of the complex conductivity of Tl-2201 calculated from the reflectivity shown in Fig. 1. Left panel: The conductivity of the optimally doped sample is punctuated by phonon peaks but is otherwise nearly flat and featureless. Right panel: The over-doped sample shows the same phonon peaks but develops a coherent, Drude-like peak for $T > T_c$ that condenses into the superfluid condensate when $T < T_c$.

FIG. 3. The ratio of the spectral weight difference $[N_N(\omega) - N_S(\omega)]$ to the superfluid density ρ_s as described in the text for optimally ($T_c = 81$ K) and over-doped ($T_c = 32$ K) Tl- 2201. The superfluid condensate is accumulated from lower energies in the over-doped sample. To calculate the over-doped curve, we extrapolated (shown as a dashed line) $\sigma_1(\omega, T = 35$ K) from $\omega = 16$ cm^{-1} to $\omega = 0$ using a Drude function with $\sigma_{dc} = 15$ (Ω cm)$^{-1}$ and $\tau^{-1} = 45$ s^{-1} and $\sigma_1(\omega, T = 5K) = 5$ (Ω cm)$^{-1}$.

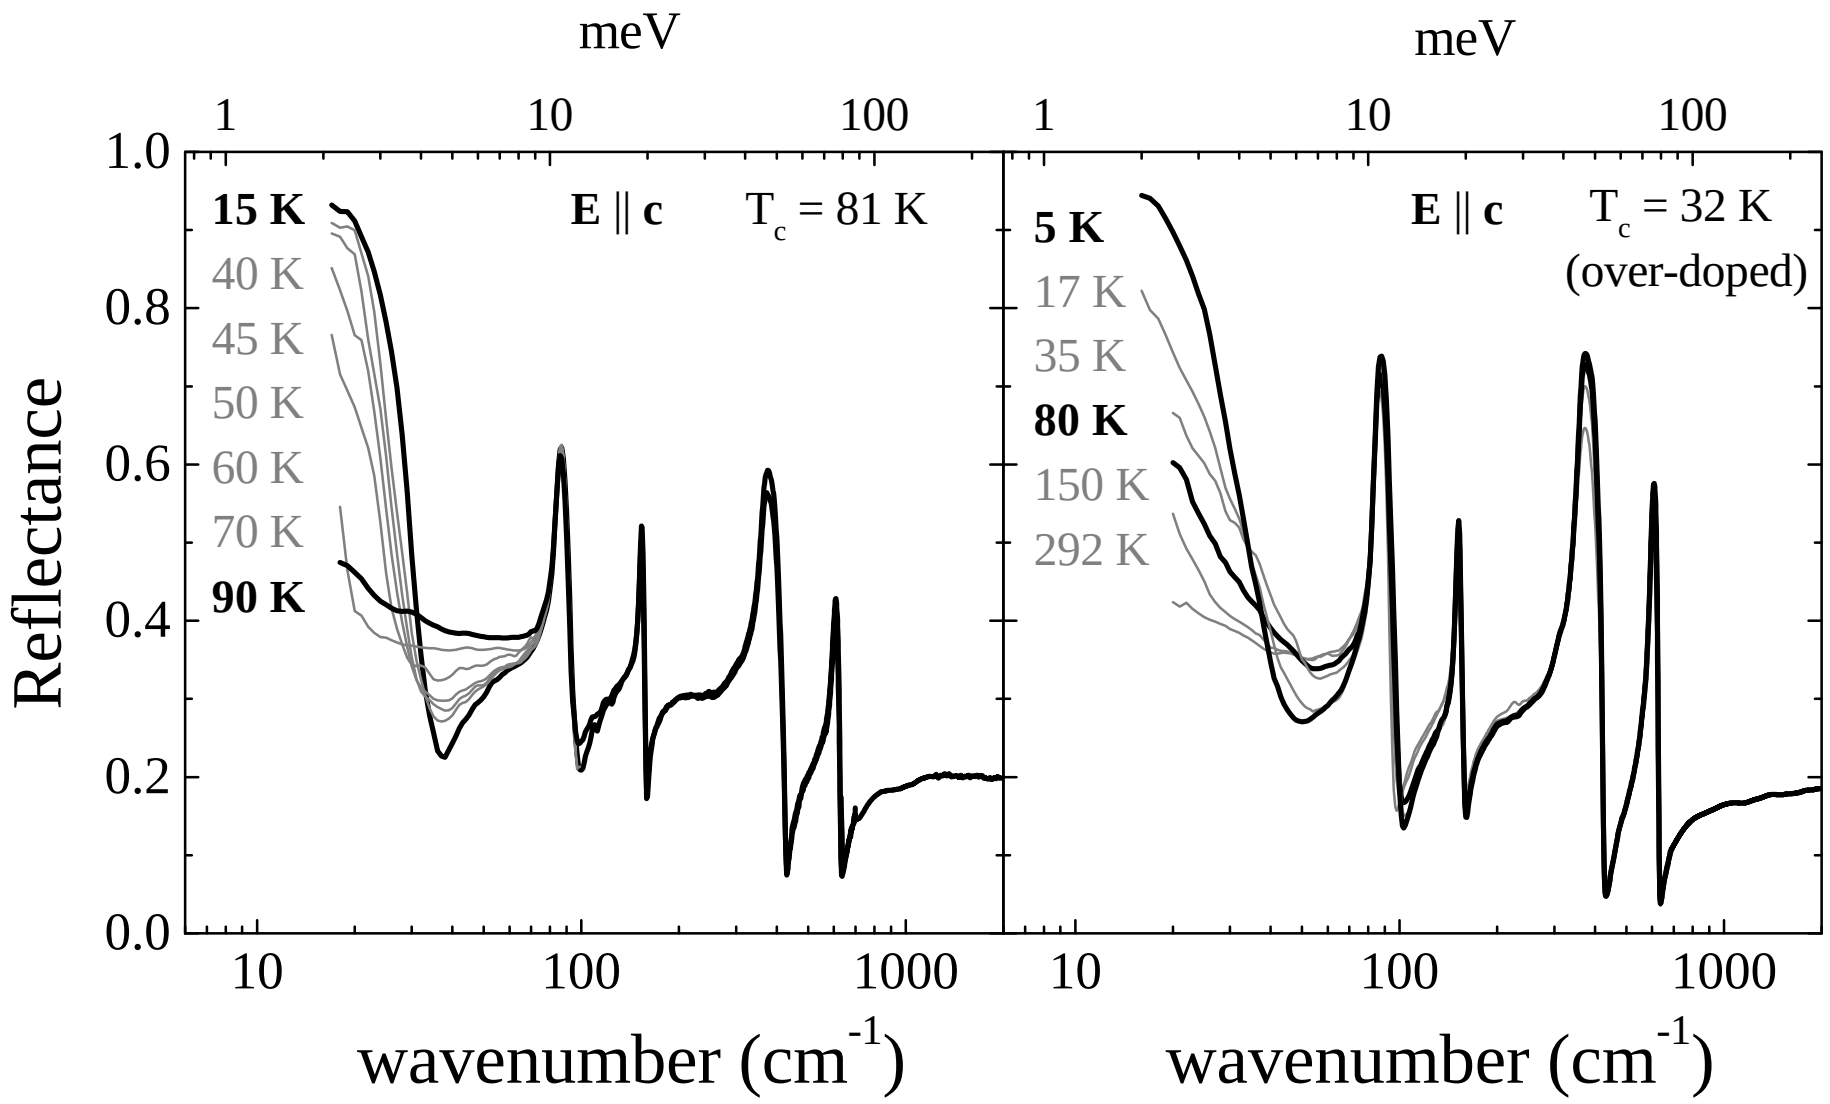

Fig. 1
A.S. Katz *et al.*
Interlayer Conductivity in the Superconductor Tl-2201

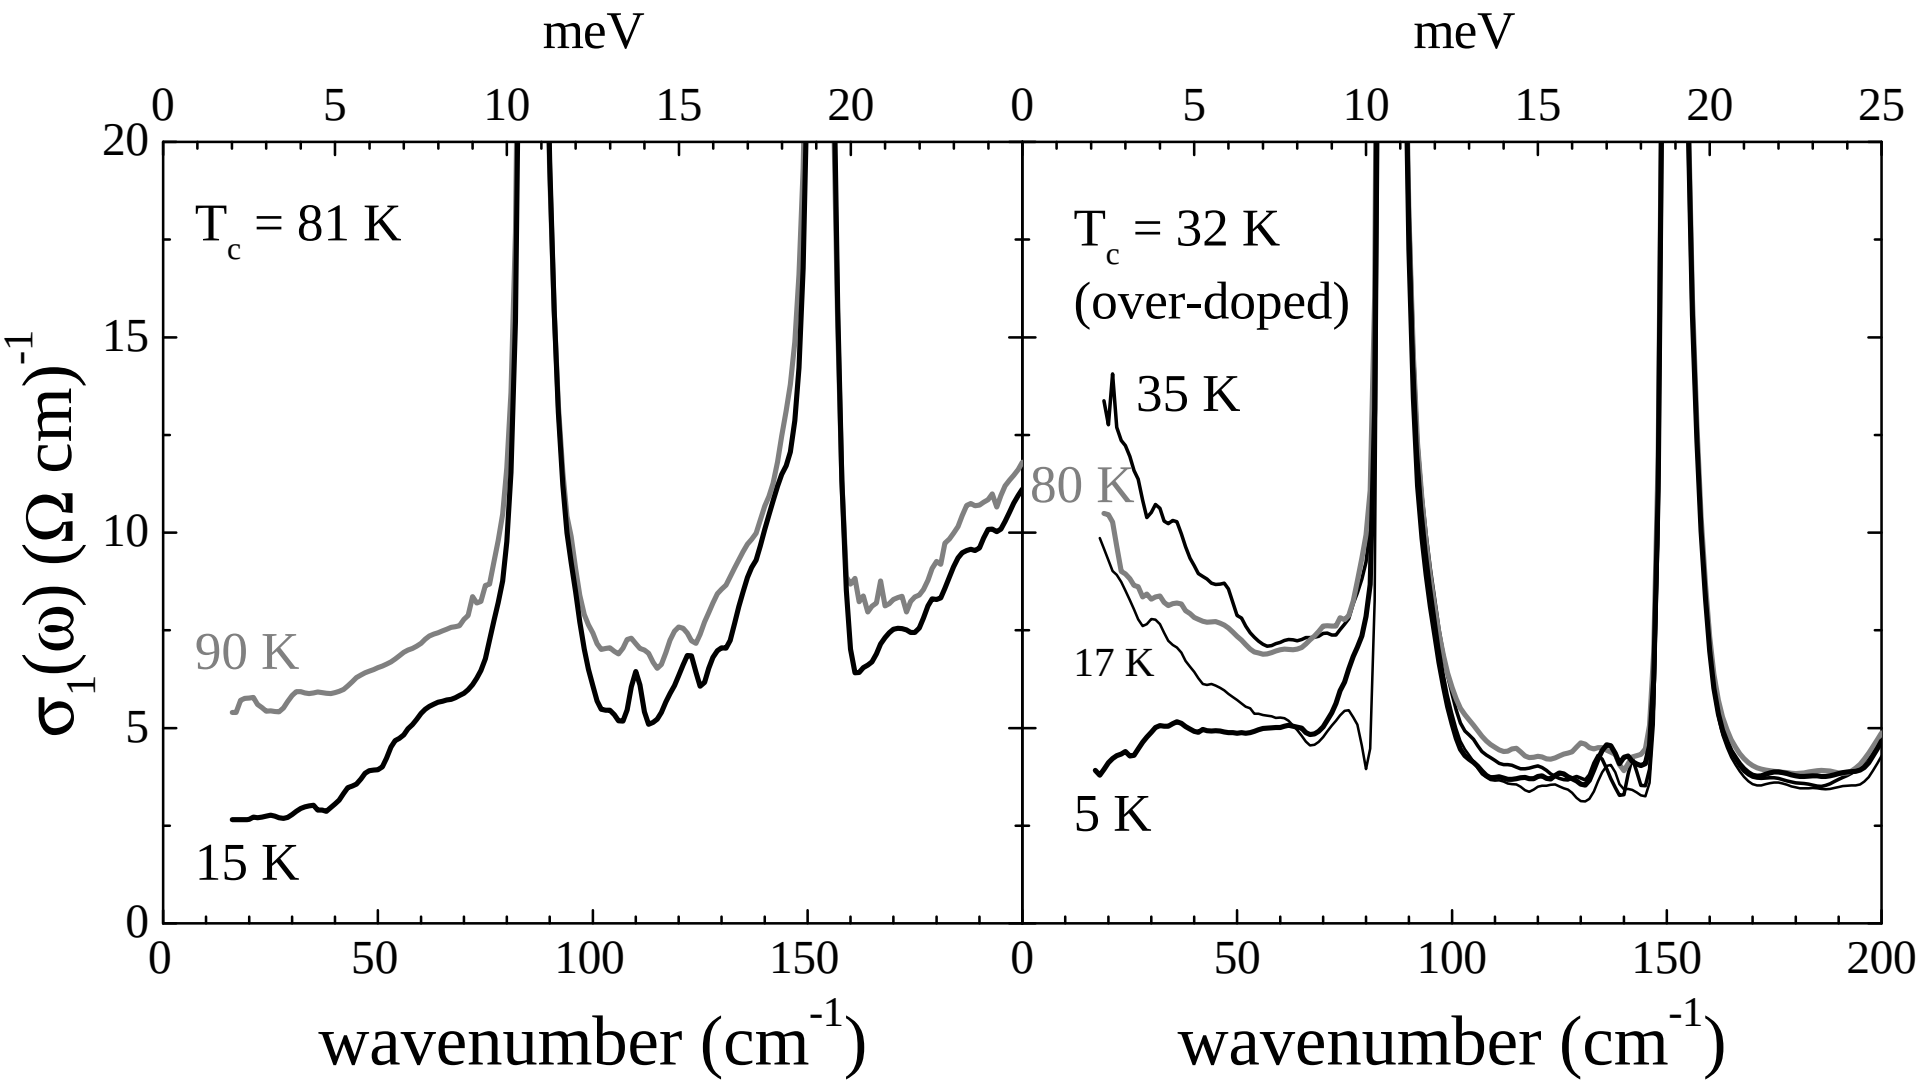

Fig. 2
A.S. Katz *et al.*
Interlayer Conductivity in the Superconductor Tl-2201

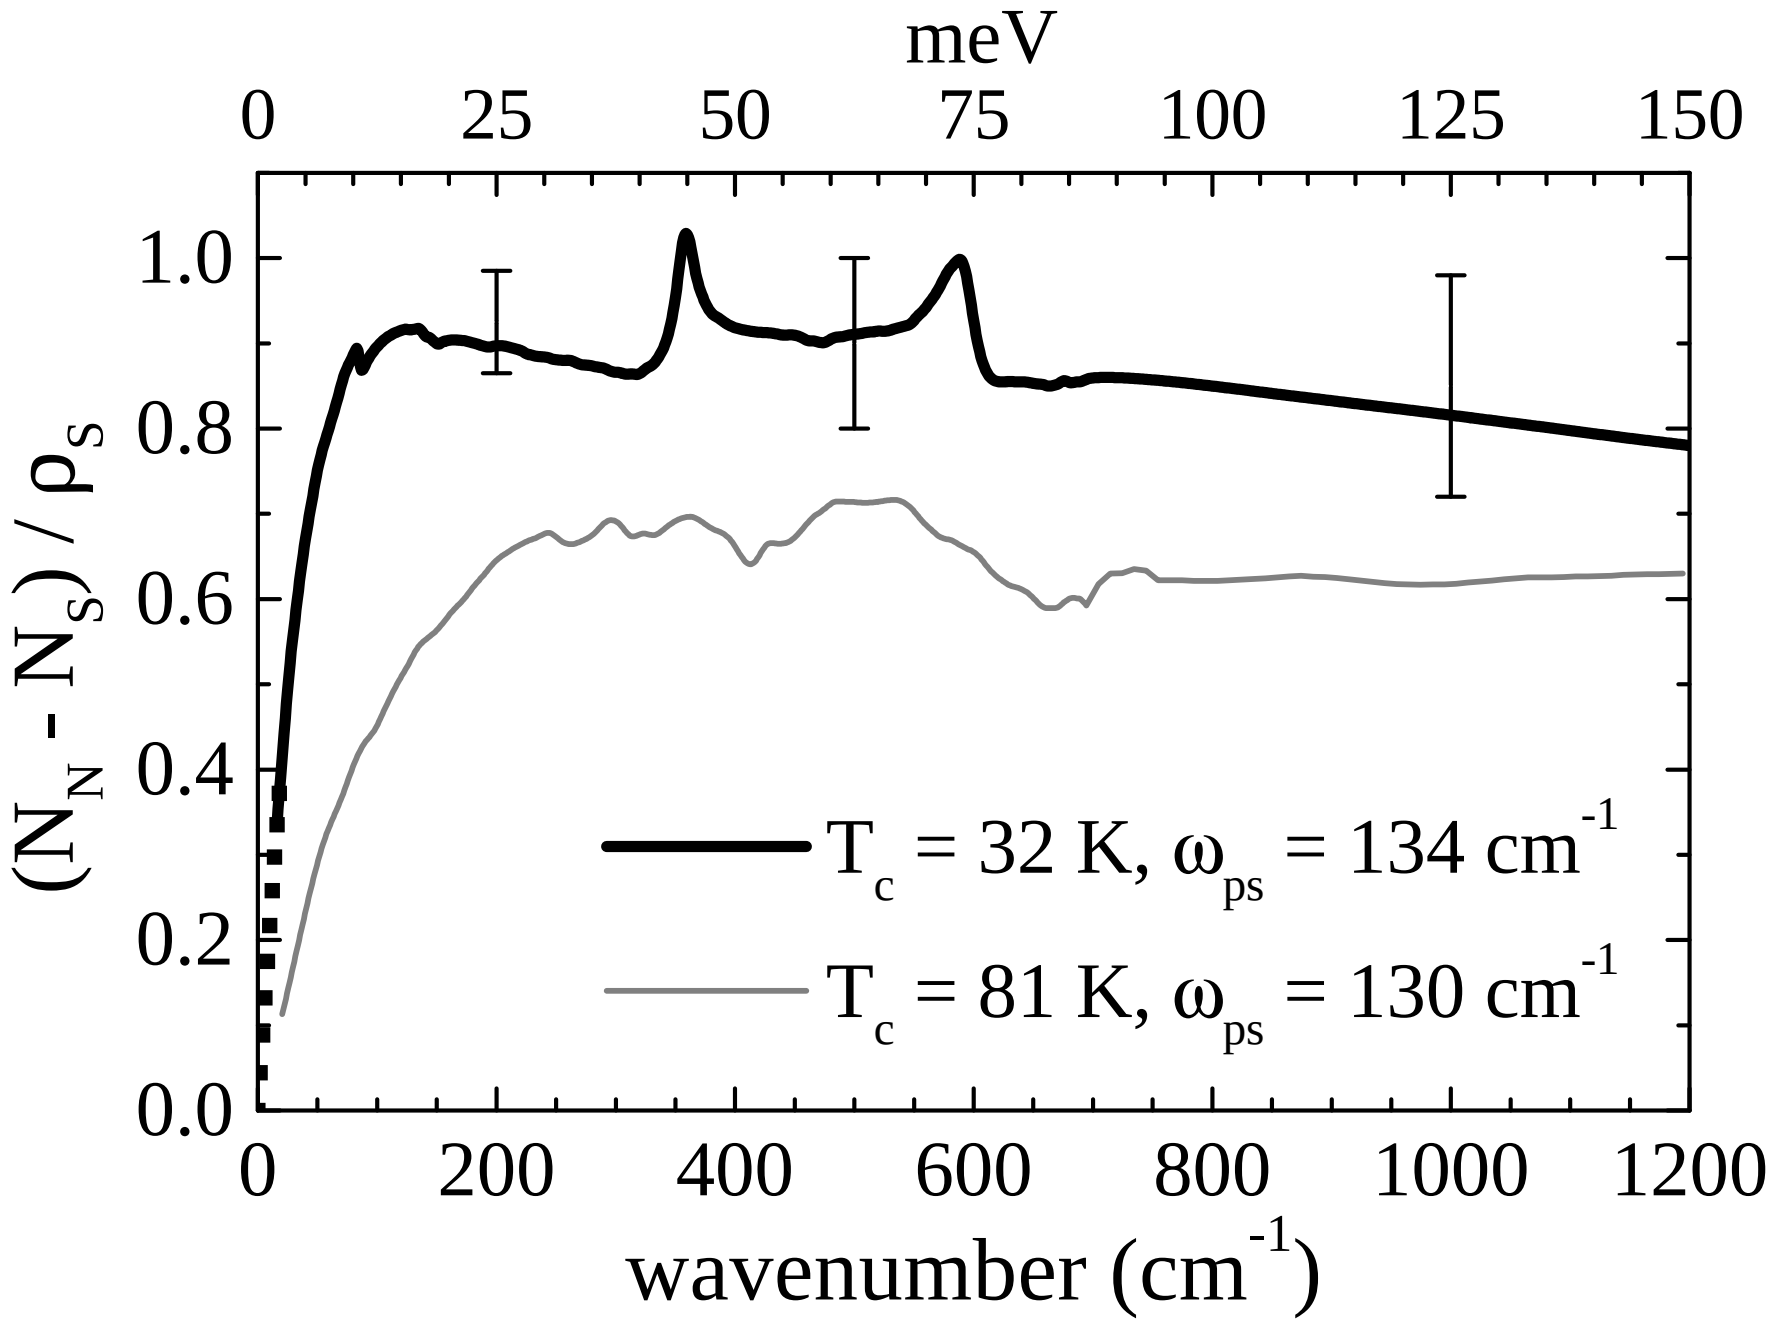

Fig. 3
A.S. Katz *et al.*
Interlayer Conductivity in the Superconductor Tl-2201